


GREEN-DRI BDK-3000 WHITE OAK DRYING TEST

NFM Report: Nov.21, 2007

Conducted by: Toyo Tex
 Drying Temperature: 40 degree C(104 degree F)
 Test Pieces: 70mm x 70mm (2 3/4" x 2 3/4") cross section White Oak Pieces

Days	0	1	2	3	4	5	6	7	8	9	10	11	12	13	14	15	16
Test Piece#																	
3	84.0%	72.2%	60.3%	48.5%	47.0%	45.5%	44.0%	37.0%	35.0%	34.5%	33.5%	32.5%	31.5%	30.5%	29.5%	28.5%	25.5%
5	78.0%	73.0%	68.0%	63.0%	60.7%	58.3%	56.0%	46.5%	41.0%	44.0%	42.2%	40.3%	38.5%	36.8%	35.0%	33.0%	30.5%
6L	106.0%	96.3%	86.7%	77.0%	76.5%	76.0%	75.5%	69.5%	46.5%	46.0%	44.7%	43.3%	42.0%	37.0%	32.0%	31.5%	29.5%
6R	71.0%	63.2%	55.3%	47.5%	42.7%	37.8%	33.0%	34.5%	32.0%	32.0%	30.7%	29.3%	28.0%	28.3%	28.5%	24.5%	21.0%
7L	96.5%	85.3%	74.2%	63.0%	59.3%	55.7%	52.0%	44.5%	44.0%	52.0%	46.3%	40.7%	35.0%	35.5%	36.0%	34.5%	20.5%
7R	96.0%	80.3%	64.7%	49.0%	50.2%	51.3%	52.5%	45.0%	40.5%	39.0%	37.3%	35.7%	34.0%	32.5%	31.0%	27.5%	26.0%
8	58.5%	53.0%	47.5%	42.0%	38.7%	35.3%	32.0%	39.0%	32.0%	32.5%	32.3%	32.2%	32.0%	30.8%	29.5%	26.0%	26.0%
9L	99.0%	83.8%	68.7%	53.5%	49.2%	44.8%	40.5%	38.0%	38.0%	37.5%	34.5%	31.5%	28.5%	27.8%	27.0%	21.0%	19.5%
9R	107.0%	97.0%	87.0%	77.0%	70.5%	64.0%	57.5%	40.0%	43.0%	36.5%	35.0%	33.5%	32.0%	26.8%	21.5%	21.5%	20.0%
10	57.5%	52.8%	48.2%	43.5%	40.7%	37.8%	35.0%	37.5%	35.5%	36.0%	34.7%	33.3%	32.0%	31.0%	30.0%	28.5%	27.0%
11	63.0%	57.5%	52.0%	46.5%	42.7%	38.8%	35.0%	35.0%	27.0%	27.0%	27.7%	28.3%	29.0%	28.5%	28.0%	26.5%	22.0%
12	62.5%	56.7%	50.8%	45.0%	41.8%	38.7%	35.5%	38.5%	31.5%	31.5%	30.3%	29.2%	28.0%	27.5%	27.0%	25.5%	25.5%
13, 29	62.0%	56.0%	50.0%	44.0%	42.7%	41.3%	40.0%	35.0%	34.5%	35.0%	33.7%	32.3%	31.0%	29.8%	28.5%	27.0%	27.0%
14L	77.0%	67.3%	57.7%	48.0%	43.2%	38.3%	33.5%	33.5%	31.5%	28.0%	27.5%	27.0%	26.5%	24.5%	22.5%	23.5%	19.0%
14R	100.0%	92.8%	85.7%	78.5%	71.0%	63.5%	56.0%	55.0%	44.5%	46.5%	42.7%	38.8%	35.0%	29.8%	24.5%	27.0%	16.0%
15L	69.0%	56.7%	44.3%	32.0%	30.8%	29.7%	28.5%	29.5%	27.5%	27.5%	25.7%	23.8%	22.0%	20.3%	18.5%	18.0%	14.5%
15R	102.0%	88.8%	75.7%	62.5%	55.2%	47.8%	40.5%	40.0%	37.0%	35.0%	32.3%	29.7%	27.0%	24.0%	21.0%	20.5%	19.5%
17	61.0%	55.0%	49.0%	43.0%	41.5%	40.0%	38.5%	37.0%	35.0%	34.0%	33.0%	32.0%	31.0%	29.8%	28.5%	28.0%	26.5%
18	62.5%	56.7%	50.8%	45.0%	43.5%	42.0%	40.5%	37.0%	33.5%	35.0%	34.0%	33.0%	32.0%	30.5%	29.0%	28.0%	27.5%
20L	87.0%	72.7%	58.3%	44.0%	42.8%	41.7%	40.5%	39.5%	39.0%	32.5%	31.7%	30.8%	30.0%	27.8%	25.5%	23.5%	21.0%
20R	87.5%	80.3%	73.2%	66.0%	60.8%	55.7%	50.5%	50.0%	48.5%	48.0%	45.2%	42.3%	39.5%	37.8%	36.0%	34.0%	32.0%
21L	91.0%	75.8%	60.7%	45.5%	42.0%	38.5%	35.0%	39.0%	29.0%	27.0%	25.0%	23.0%	21.0%	20.5%	20.0%	18.5%	13.5%
21R	91.0%	82.3%	73.7%	65.0%	54.3%	43.7%	33.0%	33.5%	31.0%	28.5%	28.0%	27.5%	27.0%	23.8%	20.5%	20.5%	15.0%
22	52.5%	48.7%	44.8%	41.0%	41.2%	41.3%	41.5%	37.0%	32.0%	34.0%	33.3%	32.7%	32.0%	31.0%	30.0%	27.5%	27.0%
23	76.0%	70.3%	64.7%	59.0%	54.2%	49.3%	44.5%	41.0%	39.5%	34.0%	34.3%	34.7%	35.0%	32.8%	30.5%	32.0%	29.0%
24	76.5%	65.0%	53.5%	42.0%	41.2%	40.3%	39.5%	45.5%	41.5%	34.5%	34.7%	34.8%	35.0%	32.3%	29.5%	30.5%	24.5%
25	60.0%	55.8%	51.7%	47.5%	43.7%	39.8%	36.0%	37.0%	35.0%	35.0%	33.5%	32.0%	30.5%	29.0%	27.5%	27.5%	24.5%
26	58.0%	53.3%	48.7%	44.0%	41.5%	39.0%	36.5%	38.0%	34.5%	28.5%	29.2%	29.8%	30.5%	29.1%	27.6%	26.5%	22.5%
27L	84.0%	76.0%	68.0%	60.0%	52.7%	45.3%	38.0%	36.5%	30.5%	22.5%	24.3%	26.2%	28.0%	26.3%	24.5%	23.0%	12.5%
27R	94.0%	84.7%	75.3%	66.0%	61.2%	56.3%	51.5%	39.5%	33.0%	30.5%	28.8%	27.2%	25.5%	22.8%	20.0%	19.0%	14.5%
28	61.5%	55.5%	49.5%	43.5%	44.0%	44.5%	45.0%	35.0%	33.5%	35.5%	33.7%	31.8%	30.0%	29.3%	28.5%	26.5%	25.5%
30	54.5%	53.5%	52.5%	51.5%	47.5%	43.5%	39.5%	36.5%	34.5%	36.5%	34.8%	33.2%	31.5%	30.3%	29.0%	28.0%	26.0%
31	77.0%	68.8%	60.7%	52.5%	49.3%	46.2%	43.0%	43.0%	37.5%	40.5%	38.3%	36.2%	34.0%	32.5%	31.0%	30.0%	23.0%
32	62.5%	57.7%	52.8%	48.0%	43.8%	39.7%	35.5%	31.0%	30.5%	30.0%	30.0%	30.0%	30.0%	28.8%	27.5%	27.5%	22.0%
35	62.5%	53.0%	43.5%	34.0%	32.8%	31.7%	30.5%	31.0%	28.0%	28.0%	28.0%	28.0%	28.0%	25.5%	23.0%	21.0%	20.0%
36L	95.5%	83.8%	72.2%	60.5%	58.8%	57.2%	55.5%	50.0%	48.0%	46.5%	43.3%	40.2%	37.0%	34.8%	32.5%	30.0%	25.5%
36R	86.0%	75.0%	64.0%	53.0%	50.3%	47.7%	45.0%	41.0%	42.5%	29.0%	30.2%	31.3%	32.5%	30.5%	28.5%	25.5%	22.0%
40	76.5%	62.0%	47.5%	33.0%	37.3%	41.7%	46.0%	35.0%	34.5%	33.5%	32.0%	30.5%	29.0%	27.0%	25.0%	22.0%	18.0%
41	74.5%	63.8%	53.2%	42.5%	41.7%	40.8%	40.0%	41.0%	38.5%	32.0%	32.5%	33.0%	33.5%	30.3%	27.0%	26.5%	19.5%
42	79.5%	69.0%	58.5%	48.0%	44.7%	41.3%	38.0%	41.0%	32.5%	36.5%	35.7%	34.8%	34.0%	31.5%	29.0%	28.5%	21.0%
Average	77.5%	68.8%	60.1%	51.4%	48.3%	45.3%	42.3%	39.8%	36.1%	34.8%	33.6%	32.4%	31.2%	29.4%	27.5%	26.2%	22.5%

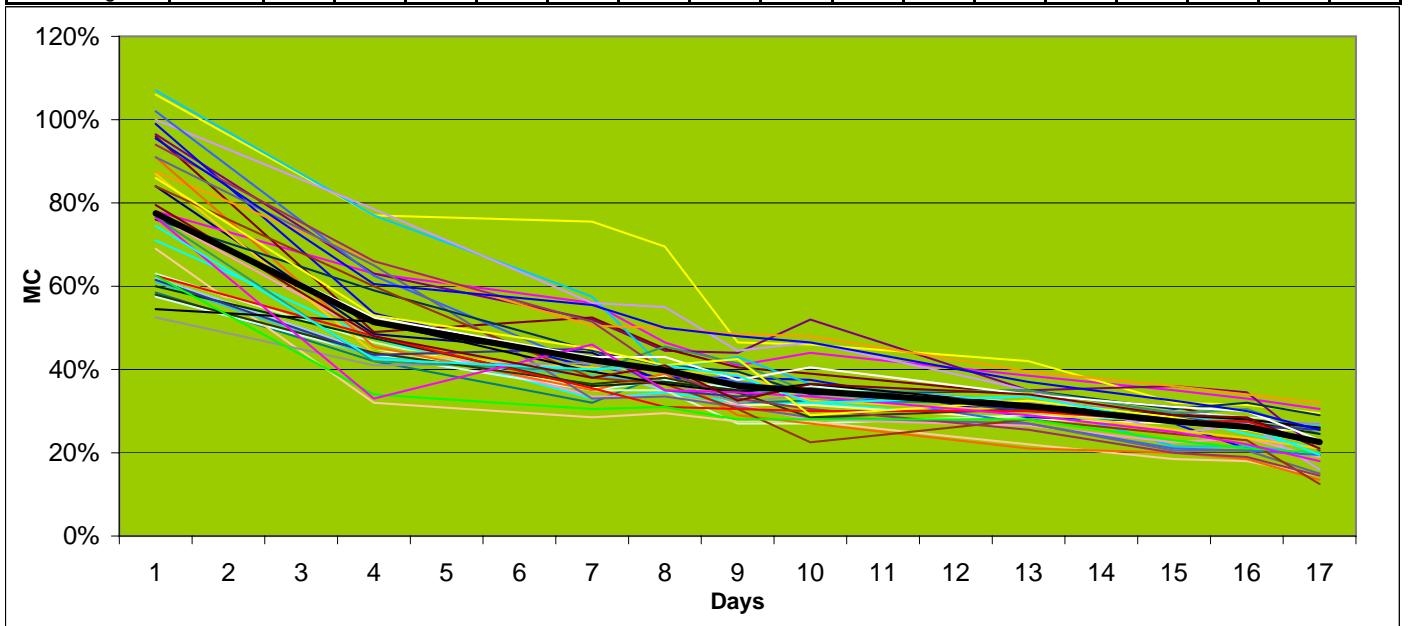

PHOTOS

